

AD 652574

**Columbia University
in the City of New York**

**DEPARTMENT OF CIVIL ENGINEERING
AND ENGINEERING MECHANICS**

INSTITUTE FOR THE STUDY OF FATIGUE AND RELIABILITY



**INSTABILITY OF TITANIUM AND Ti/6Al/4V ALLOY
AT ROOM TEMPERATURE**

by

W. A. Wood

Sponsoring Agencies
Office of Naval Research
Air Force Materials Laboratory
Advanced Research Projects Agency

DDC
RECEIVED
JUN 6 1967

Contract No. NONR 266(91)
Project No. NR 064-470

Technical Report No. 45

April 1967

Reproduction in whole or in part is permitted for any purpose
of the United States Government

ARCHIVE COPY

STATEMENT NO. 1

Distribution of This Document is Unlimited

**Columbia University
in the City of New York**

**DEPARTMENT OF CIVIL ENGINEERING
AND ENGINEERING MECHANICS**

INSTITUTE FOR THE STUDY OF FATIGUE AND RELIABILITY



**INSTABILITY OF TITANIUM AND Ti/6Al/4V ALLOY
AT ROOM TEMPERATURE**

by

W. A. Wood

Sponsoring Agencies
Office of Naval Research
Air Force Materials Laboratory
Advanced Research Projects Agency

Contract No. NONR 266(91)
Project No. NR 064-470

Technical Report No. 45

April 1967

Reproduction in whole or in part is permitted for any purpose
of the United States Government

Publications of the Institute for the Study of Fatigue and Reliability

No.

- 1) Shinozuka, M. On Upper and Lower Bounds of the Probability of Failure of Simple Structures under Random Excitation. December 1963.
- 2) Freudenthal, A.M., Weibull, W. and Payne, A.O. First Seminar on Fatigue and Fatigue Design. December 1963.
- 3) Wood, W.A., Reimann, W.H. and Sargent, K.R. Comparison of Fatigue Mechanisms in Bcc Iron and Fcc Metals. April 1964.
- 4) Heller, R.A. and Shinozuka, M. Development of Randomized Load Sequences with Transition Probabilities Based on a Markov Process. June 1964.
- 5) Branger, J. Second Seminar on Fatigue and Fatigue Design. June 1964.
- 6) Wood, W.A. and Reimann, W.H. Room Temperature Creep in Iron under Tensile Stress and a Superposed Alternating Torsion. June 1964.
- 7) Ronay, M., Reimann, W.H. and Wood, W.A. Mechanism of Fatigue Deformation at Elevated Temperature. June 1964.
- 8) Freudenthal, A.M. and Shinozuka, M. Upper and Lower Bounds of Probability of Structural Failure under Earthquake Acceleration. June 1964.
- 9) Ronay, M. On Strain Incompatibility and Grain Boundary Damage in Fatigue. August 1964.
- 10) Shinozuka, M. Random Vibration of a Beam Column. October 1964.
- 11) Wood, W.A. and Reimann, W.H. Some direct Observations of Cumulative Fatigue Damage in Metals. October 1964.
- 12) Freudenthal, A.M., Garrelts, J.M. and Shinozuka, M. The Analysis of Structural Safety. October 1964.
- 13) Ronay, M. and Freudenthal, A.M. Second Order Effects in Dissipative Solids. January 1965.
- 14) Shinozuka, M. and Nishimura, A. On General Representation of a Density Function. February 1965.
- 15) Wood, W.A. and Nine, H.D. Differences in Fatigue Behavior of Single Copper Crystals and Polycrystalline Copper at Elevated Temperatures. February 1965.

No.

- 16) Ronay, M. On Second Order Strain Accumulation in Torsion Fatigue. February 1965.
- 17) Heller, R.A. and Heller, A.S. A Probabilistic Approach to Cumulative Fatigue Damage in Redundant Structures. March 1965.
- 18) Wood, W.A. and Reimann, W.H. Extension of Copper and Brass under Tension and Cyclic Torsion. April 1965.
- 19) Grosskreutz, J.C., Reimann, W.H. and Wood, W.A. Correlation of Optical and Electron-Optical Observations in Torsion Fatigue of Brass. April 1965.
- 20) Freudenthal, A.M. and Shinozuka, M. On Fatigue Failure of a Multiple-Load-Path Redundant Structure. June 1965.
- 21) Shinozuka, M. and Yao, J.T.P. On the Two-Sided Time-Dependent Barrier Problem. June 1965.
- 22) Ronay, M. On Second Order Strain Accumulation in Aluminum in Reversed Cyclic Torsion at Elevated Temperatures. June 1965.
- 23) Freudenthal, A.M. Second Order Effects on Plasticity. August 1965.
- 24) Wood, W.A. Experimental Approach to Basic Study of Fatigue. August 1965.
- 25) Ronay, M. Conditions of Interaction of Cyclic Torsion with Axial Loads. August 1965.
- 26) Heller, R.A., and Donat, R.C. Experiments on the Fatigue Failure of a Redundant Structure. October 1965.
- 27) Shinozuka, M., Yao, J.T.P. and Nishimura, A. A Note on the Reliability of Redundant Structures. November 1965.
- 28) Mason, W.P. Internal Friction Measurements and Their Uses in Determining the Interaction of Acoustic Waves With Phonons, Electrons and Dislocations. January 1966.
- 29) Shinozuka, M., Hakuno, M. and Itagaki, H. Response of a Multi-Story Frame Structure to Random Excitation. February 1966.

No.

- 30) Wood, W. A., Suppression of Creep Induced by Cyclic Torsion in Copper under Tension. April 1966.
- 31) Shinozuka, M. and Sato, Y., On the Numerical Simulation of Nonstationary Random Processes. April 1966.
- 32) Mason, W. P., Effect of Electron-Damped Dislocations on the Determination of the Superconducting Energy Gaps of Metals. May 1966.
- 33) Murro, R. P., Creep Behavior of an Aluminum Alloy under Transient Temperatures. June 1966.
- 34) Ronay, M., On the Micro-Mechanism of Second-Order Extension of Aluminum in Reversed Cyclic Torsion. June 1966.
- 35) Wood, W. A., Yield and Second-Order Effects Induced by Cyclic Torsion in Copper under Tension. June 1966.
- 36) Nine, H. D., and Wood, W. A., On Improvement of Fatigue Life by Dispersal of Cyclic Strain. July 1966.
- 37) Jacoby, G., Review of Fractographic Analysis Methods for Fatigue Fracture Surfaces. July 1966.
- 38) Donat, R. C. and Heller, R. A., Experiment on a Fail Safe Structural Model. September 1966.
- 39) Freudenthal, A. M., and Gou, P. F., Accumulation of Second Order Strain in Cyclic Loading of Viscous Bar. September 1966.
- 40) Mason, W. P., Acoustic Waves and Dislocation Motions. October 1966.
- 41) Mason, W. P., and Bateman, T. B., Relation between Third-order Elastic Moduli and the Thermal Attenuation of Ultrasonic Waves in Nonconducting and Metallic Crystals. October 1966.
- 42) Wood, W. A., Re-examination of Mechanical Hysteresis. February, 1967.
- 43) Mason, W. P., and Rosenberg, A., Phonon and Electron Drag Coefficients in Single-crystal Aluminum. November 1966.
- 44) Mason, W. P., Mechanical Instability of Alloy Ti-6Al-4V Under Large Extensional Vibrations. February 1967.

ABSTRACT

Titanium and Ti/6Al/4V under torsion exhibit unusual instability which shows itself as (a) abnormally prolonged creep on yielding, (b) ineffective strain-hardening after yielding, and (c) deviations from elastic strain at loads above a limit of proportionality which is low compared with the bulk yield stress. As a result of this inherent instability it is possible to produce significant axial extensions under low tensile stresses combined with small-amplitude cyclic torsion; and to reduce the nominal bulk yield stress in torsion to at least half its nominal value by suitable prior straining.

1. Introduction

Alpha-titanium loaded in torsion to or beyond its bulk yield-point at room temperature creeps abnormally. Typical creep curves are shown in Fig. 1 for commercially pure titanium in the form of tubular specimens obtained by turning, boring, and reamering 5/16 in. diameter rod to smoothly finished test portions 1 1/2 in. long, 1/4 in. o.d., and 3/16 in. i.d. The twist in these curves is plotted in degrees, since degrees gives a ready picture of its extent, but it can be expressed as shear strain by the relation 1 degree twist equals 0.00145 surface shear.

This creep is plotted only to 300 hours but actually was measured up to 700 hours, or until it caused undue buckling of a specimen, and though it had slowed down it was still in progress at the end of each test. This creep too refers to titanium which had been annealed in vacuo for 1/2 hour at 1300°F, but it appeared equally in unheated specimens and in specimens which were solid. Thus it seems that alpha-titanium in any form when strained above the yield becomes unstable, basically because it is incapable of strain-hardening effectively.

It was of interest therefore to test how stable the alpha-titanium might be when strained below the yield and also to test alloys containing alpha-titanium as a constituent phase. The alloy reported

on here is Ti/6Al/4V (AMS 4928), reduced like the titanium from 5/16 in. rod to similar tubular specimens and similarly tested in dead loading.

2. Pseudo-Elastic Range (Titanium)

An outstanding feature of titanium loaded below its yield was a low limit of proportionality relative to its bulk yield. This feature is illustrated by the torque/twist curve in Fig. 2 which shows an L.P. ~ 18 lb.-in. and a yield ~ 50 lb.-in. Because the metal thus exhibited a long drawn-out range between L.P. and yield it also exhibited easily observed permanent sets on unloading from points within this range, for example from points A and B in Fig. 2. Moreover a specimen on re-loading to A or B showed a small increment of strain as a result of the cycle, an irreversibility, clear at point B for example, which confirmed that the true linear elastic range of the metal was not as extensive as its high yield point might suggest.

3. Pseudo-Elastic Range (Ti/6Al/4V)

The alloy showed even more marked evidence of the above pseudo-elasticity because its yield, but not its L.P., was much higher than that of the pure metal; so that the range between L.P. and yield was drawn out even more. This range is illustrated by Fig. 3, the L.P. now being only about 1/10th of the yield point. Consequently, as

Fig. 3 also illustrates, unloading from points such as A, B, C, D, in this range led to obvious permanent sets.

Fig. 3 refers to a specimen which was not heat treated after machining and which therefore might be taken as characteristic of a cold-worked state. However, specimens which were heat treated showed essentially similar effects, though their yield point and L.P. might be lowered a little by the heating. For example, as shown by Fig. 4, similar effects occurred in specimens heated in vacuo for 1 hour at 1300°F . Other heat treatments were 1 hour at 1200°F , 3 hours at 1200°F , 3 hours at 1300°F ; so the effects were characteristic of the material and not of any particular heat treatment. Fig. 4 also serves to illustrate further that the process of unloading and re-loading from points such as A, B, C itself produces an increment of strain; thus the point B from which an unloading began does not lie on the re-loading curve to C, a further confirmation of the pseudo-elasticity.

4. Cycles of Torsion Combined With Axial Tension

If a specimen were truly elastic in torsion up to a yield torque T_0 and in tension to yield σ_0 it should be elastic also under combinations of T and σ corresponding to points within a Mises type ellipse with axes T_0 and σ_0 , as depicted in Fig. 5a; and it should remain elastic when T is reversed to $-T$. If however it is beyond its elastic range under the combination T, σ it should exhibit a permanent axial

extension when T is reversed. Such extension provides a sensitive indication of deviations from elasticity because it is additive in successive reversals.

This test was applied to the alloy at T, σ combinations well within the above type of ellipse. Nominal tensile yield according to the suppliers was 130,000 to 140,000 psi, so the σ_0 axis of the ellipse in Fig. 5a has been made equivalent to 135,000 psi. Yield in torsion according to the present tests occurred at $\theta \sim 12$ degrees and the torsion axis of the ellipse for convenience has been left in degrees, with $\theta_0 = 12$ degrees. Test points corresponded to points like P where θ was only 3 degrees and σ only 20,000 psi.

The test was applied in a machine designed for the method. Standard procedure was first to apply the axial tensile load and allow any resulting extension to come to rest; then to apply the cycles of torsion, normally at 1500 cpm. Extra extension induced by the cycles was plotted against cycles.

Fig. 5b, which shows the curve corresponding to point P, demonstrates a significantly large induced extension and so proves a marked deviation from elasticity at stresses well within the nominal yields of the alloy. Fig. 5b includes curves showing extensions at even less σ , θ values than those at P.

Thus the alloy is even more unstable when cyclic torsion is superposed on static tension than under static loading alone and unstable

moreover under combinations well within its nominal torsion and tensile yields.

5. Instability Induced By Cycles Of Large Amplitude

The initial yield torque of the alloy could be at least halved by a prior straining conveniently described by reference to Fig. 6. A specimen was first loaded in torsion to its yield T_0 , here 170 lb.-in.; then allowed to creep under T_0 through $\theta = 53$ degrees, the time taken in creep being 65 hours. It was then subjected to the reverse torque $-T_0$. As Fig. 6 indicates the specimen as a result of this reversal tended to creep at loads less than $-T_0$ and, when $-T_0$ itself was reached, crept more rapidly than previously at $+T_0$; it now crept through 53 degrees in only 23 hours. Next the load was reversed to $+T_0$ in the original direction. Creep during this reversal was further accentuated and at $+T_0$ now produced a twist of 53 degrees in only 2 hours; and so on in a second cycle.

If after a second cycle the specimen was held under torque 90 lb.-in., a load only about half of its original nominal yield T_0 , it exhibited a slow but continuous creep which did not occur before this cyclic straining; this creep is shown in Fig. 7 for the first 300 hours. Thus the nominal high yield of this alloy is not a fixed property. It may be reduced to at least half by prior treatments, here prior cycles of strain.

6. Discussion

Alpha-titanium and its alloy Ti/6Al/4V may possibly exhibit weaknesses in service because they do not strain-harden efficiently. In particular they exhibit unduly prolonged creep on yielding, so their stress/strain relationship above yield is meaningless, and they lack the safeguard of hardening which allows normal metal to adjust itself to overstrain. It appears that in assessing whether an alloy can withstand service stresses some attention should be paid not only to its yield strength but also to its capacity for strain-hardening.

It should be possible to tell why the alloy does not strain-harden efficiently from a study of its deformed microstructure. Meanwhile it seems reasonable to make the following comments, based on current theories of mechanical strength. These would attribute its high yield-strength to interstitials, impurity atoms, and phase boundaries, which strongly pin the dislocations responsible for plastic flow; yield becomes the stress needed to pluck dislocations away. In normal metal the dislocations thus set free soon become pinned again and plastic strain ceases; but not, apparently, in titanium and the alloy. An inability to pin mobile dislocations appears to be the basic cause of its special behavior.

This inability, again according to current theories, is likely to arise when interstitial and impurity atoms do not diffuse easily

to the mobile dislocations and recapture them. Such slow diffusion in titanium is perhaps to be expected, for it has strong chemical affinity for the common interstitials and impurities, oxygen, carbon, nitrogen. It might be overcome by additions of impurity atoms with less affinity.

The inability to pin dislocations could also account for specific observations. The drawn-out pseudo-elasticity between L.P. and yield would result from odd dislocations which are already free. The halving of an initially high yield stress like that described in Fig. 6 would arise because the prior creep straining at yield is likely to set free a large number of mobile dislocations; these then persist and permit plasticity under a subsequent lower stress; other prior treatments with similar results might be anticipated.

Finally it might be predicted that the instability at room temperature may diminish at higher temperatures because higher temperatures normally expedite diffusion. However, for the same reason, instability could persist at lower temperatures.

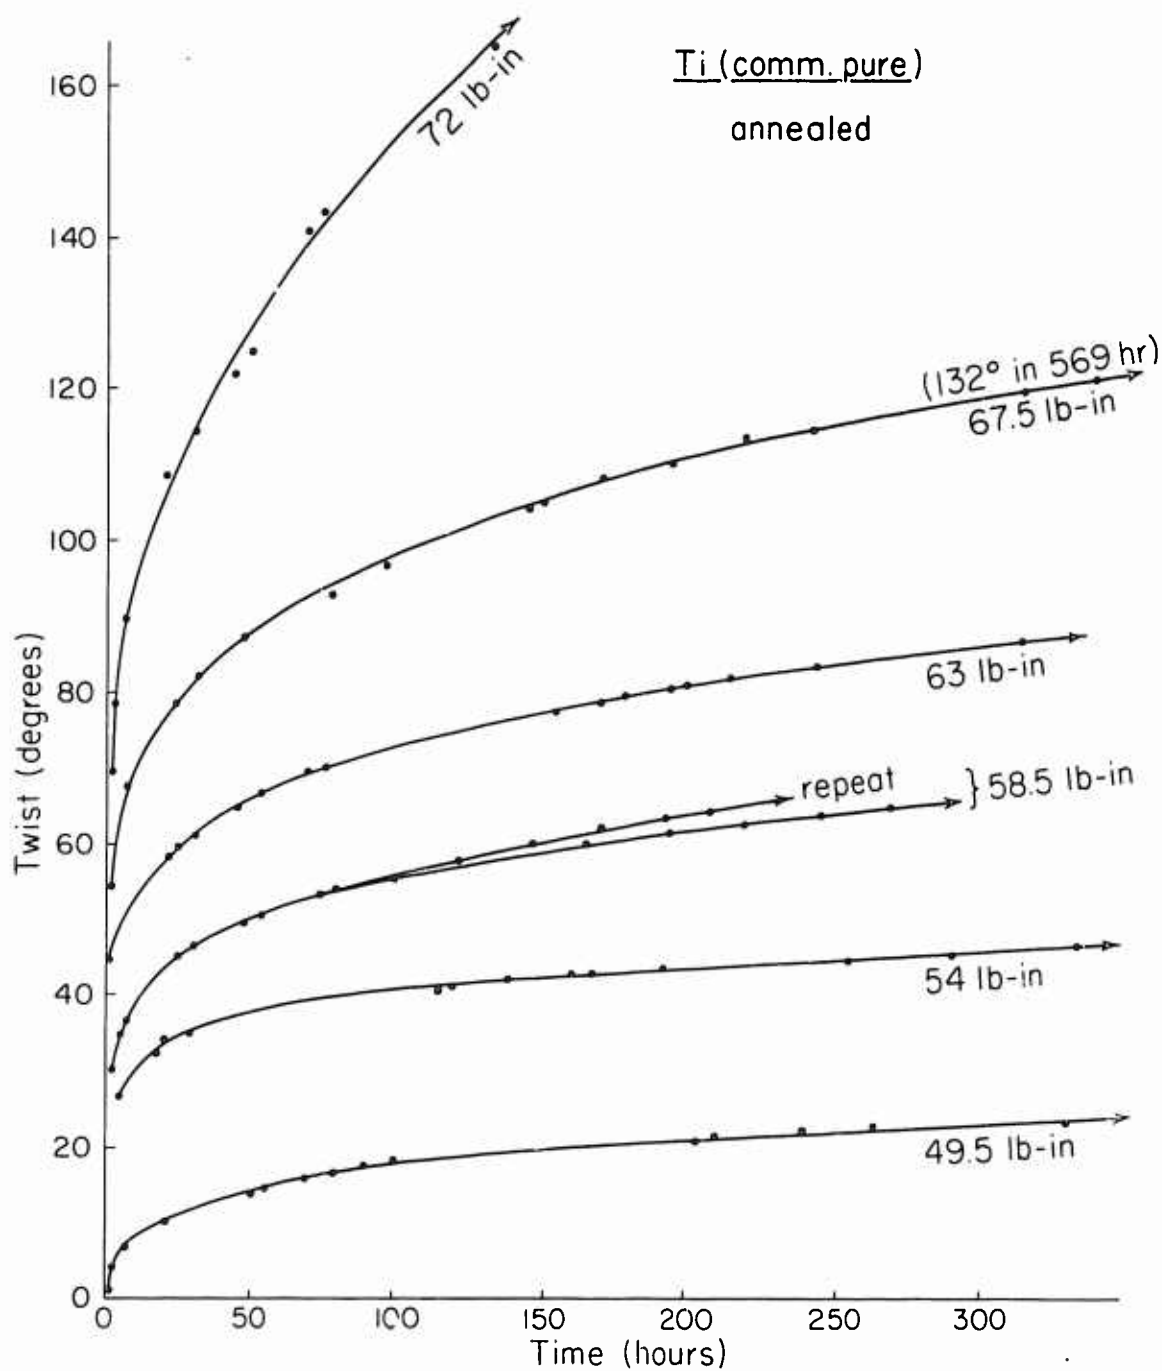


Fig. 1. Room-temperature creep of titanium at yield ~ 50 lb.-in. and above.

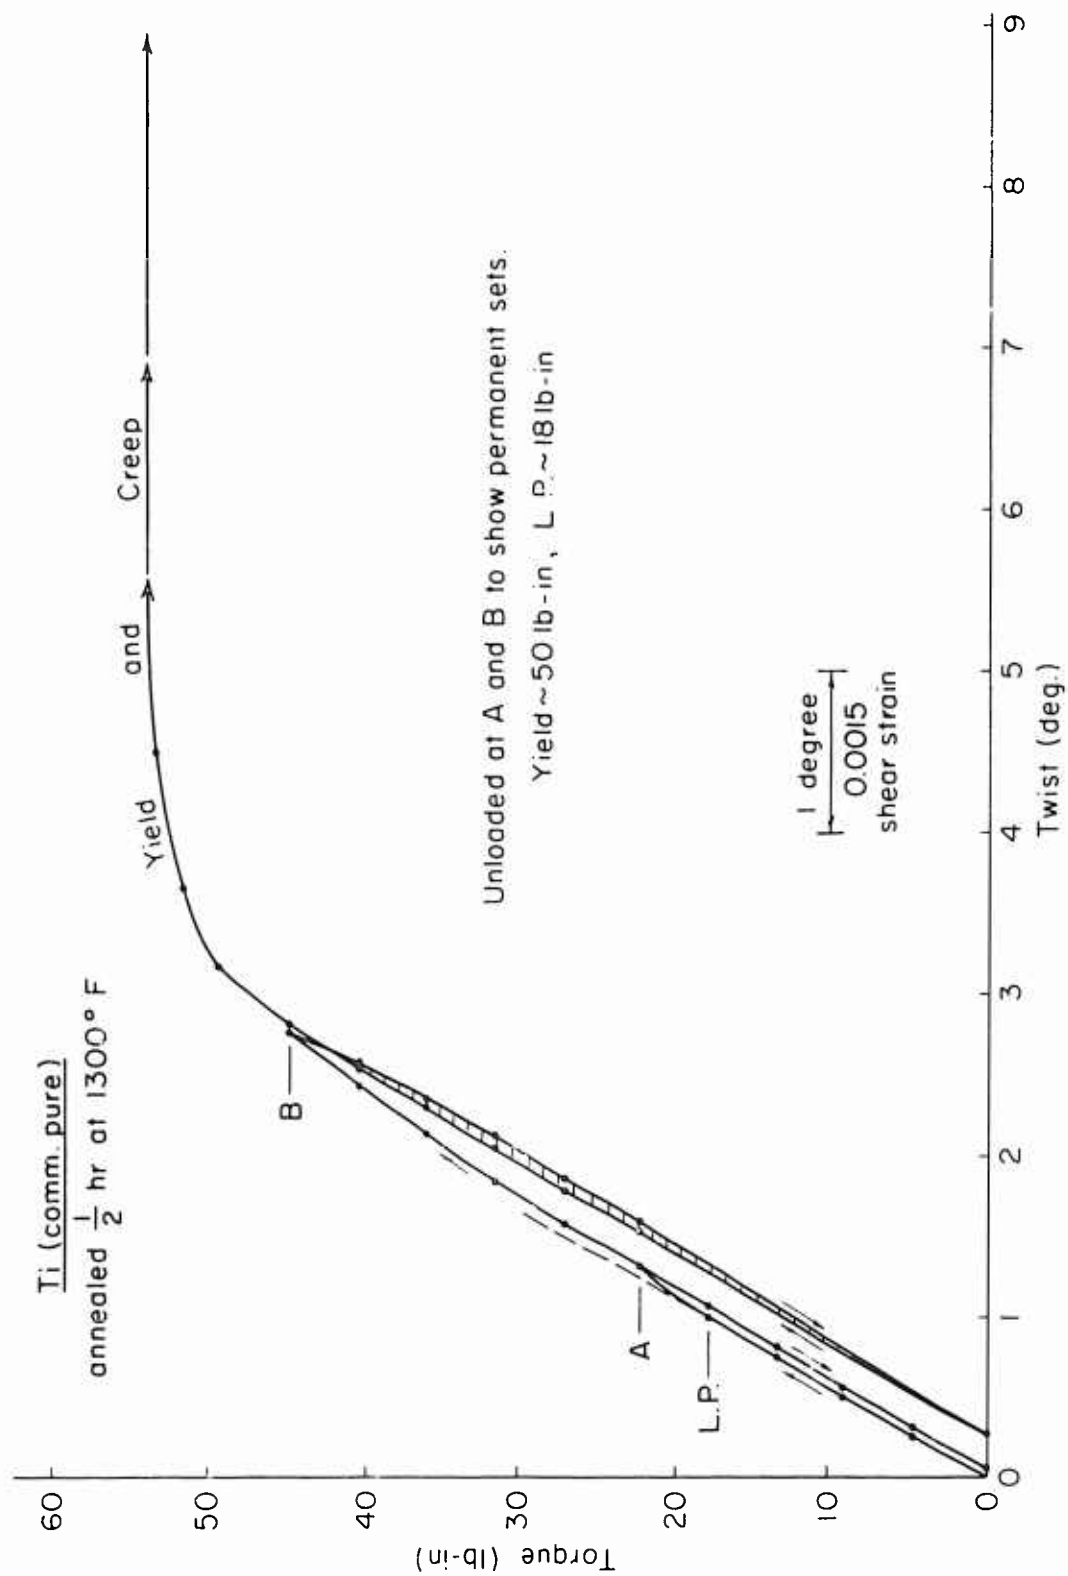


Fig. 2. Torque/twist curve of titanium showing pseudo-elastic range.

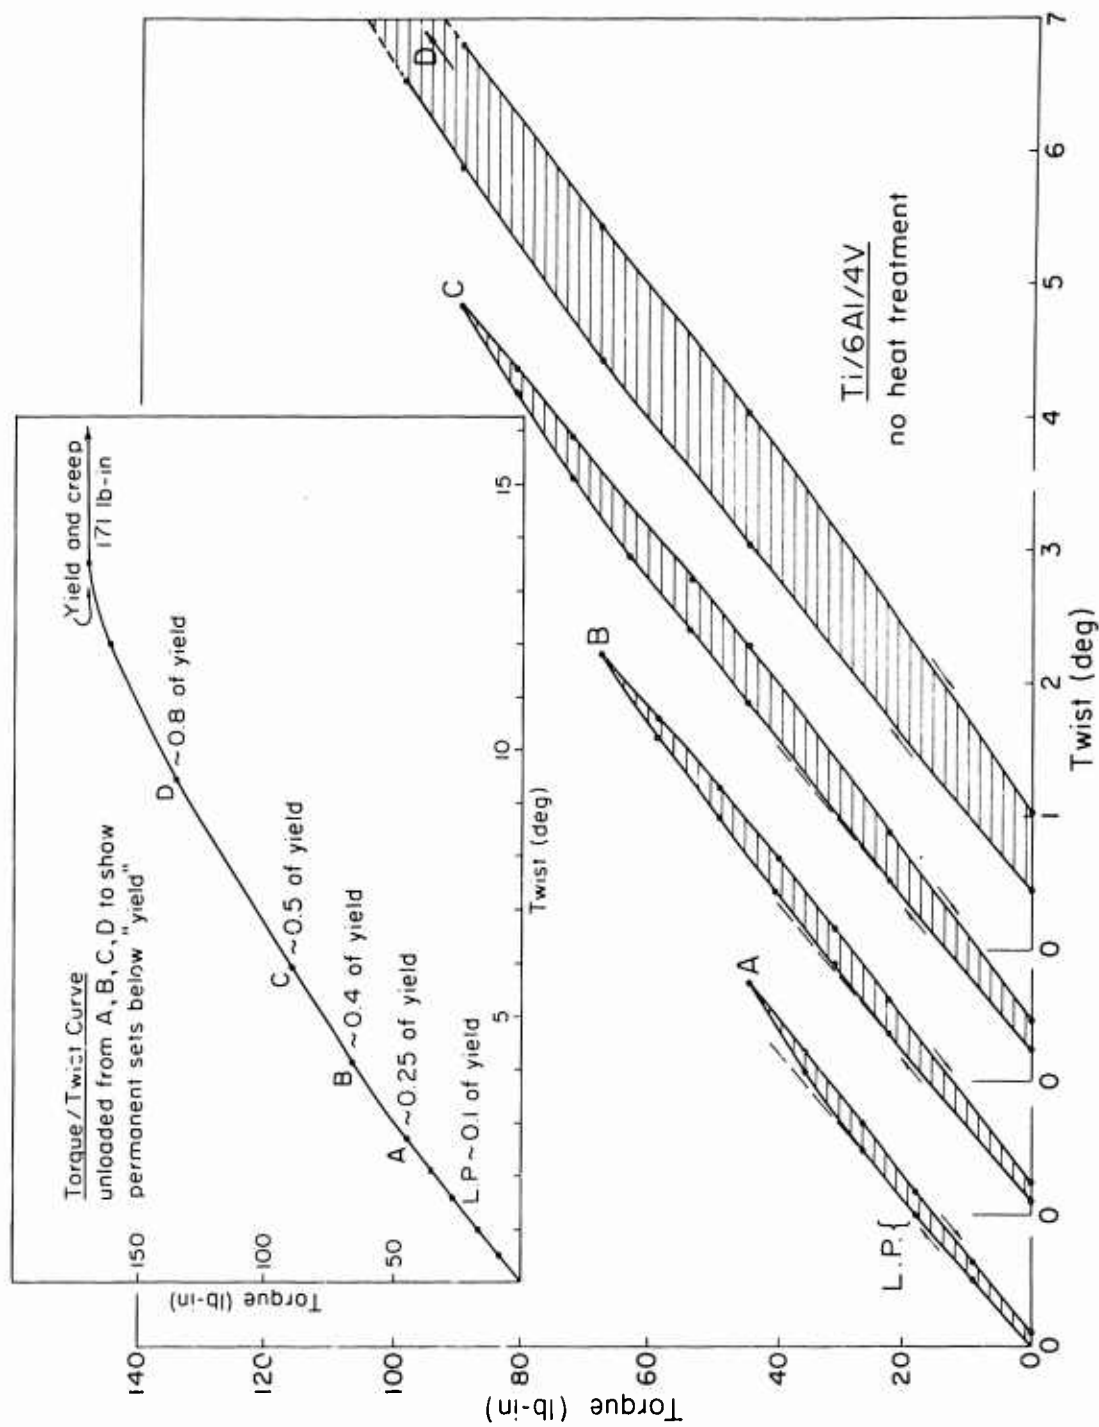


Fig. 3. Pseudo-elastic range in alloy (no heat treatment).

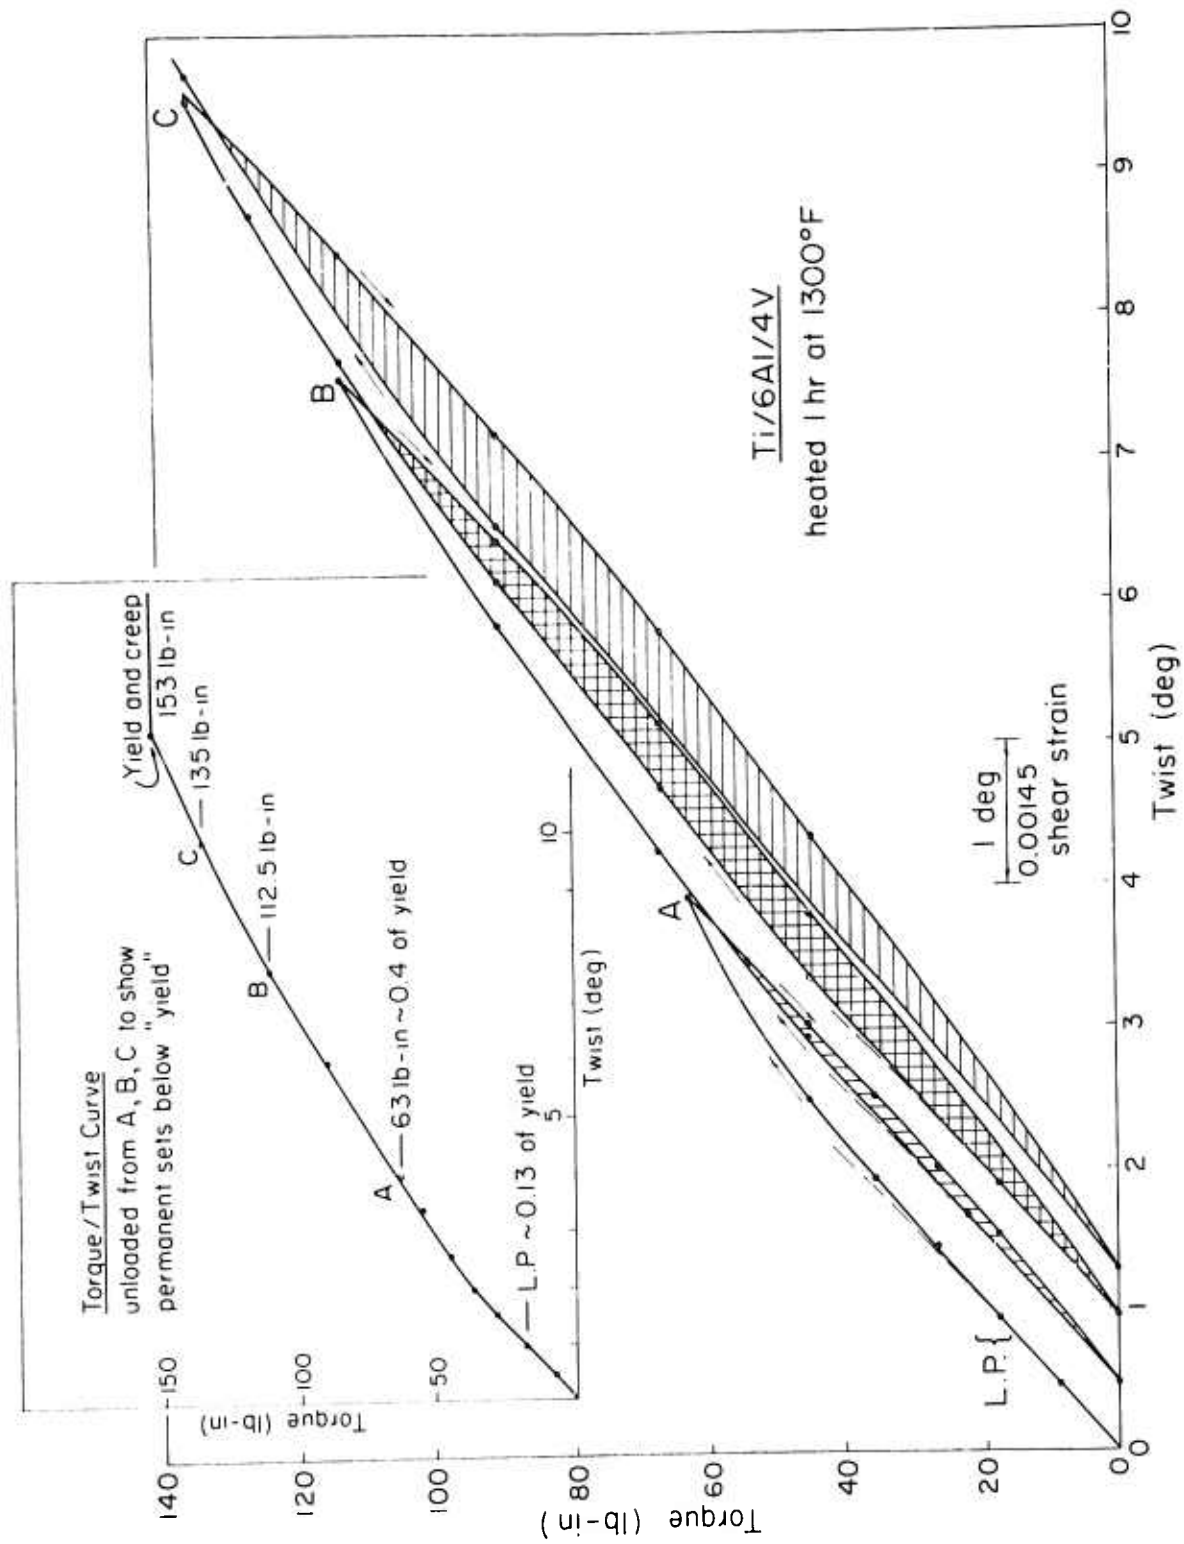


Fig. 4. Pseudo-elastic range in alloy (heat treated).

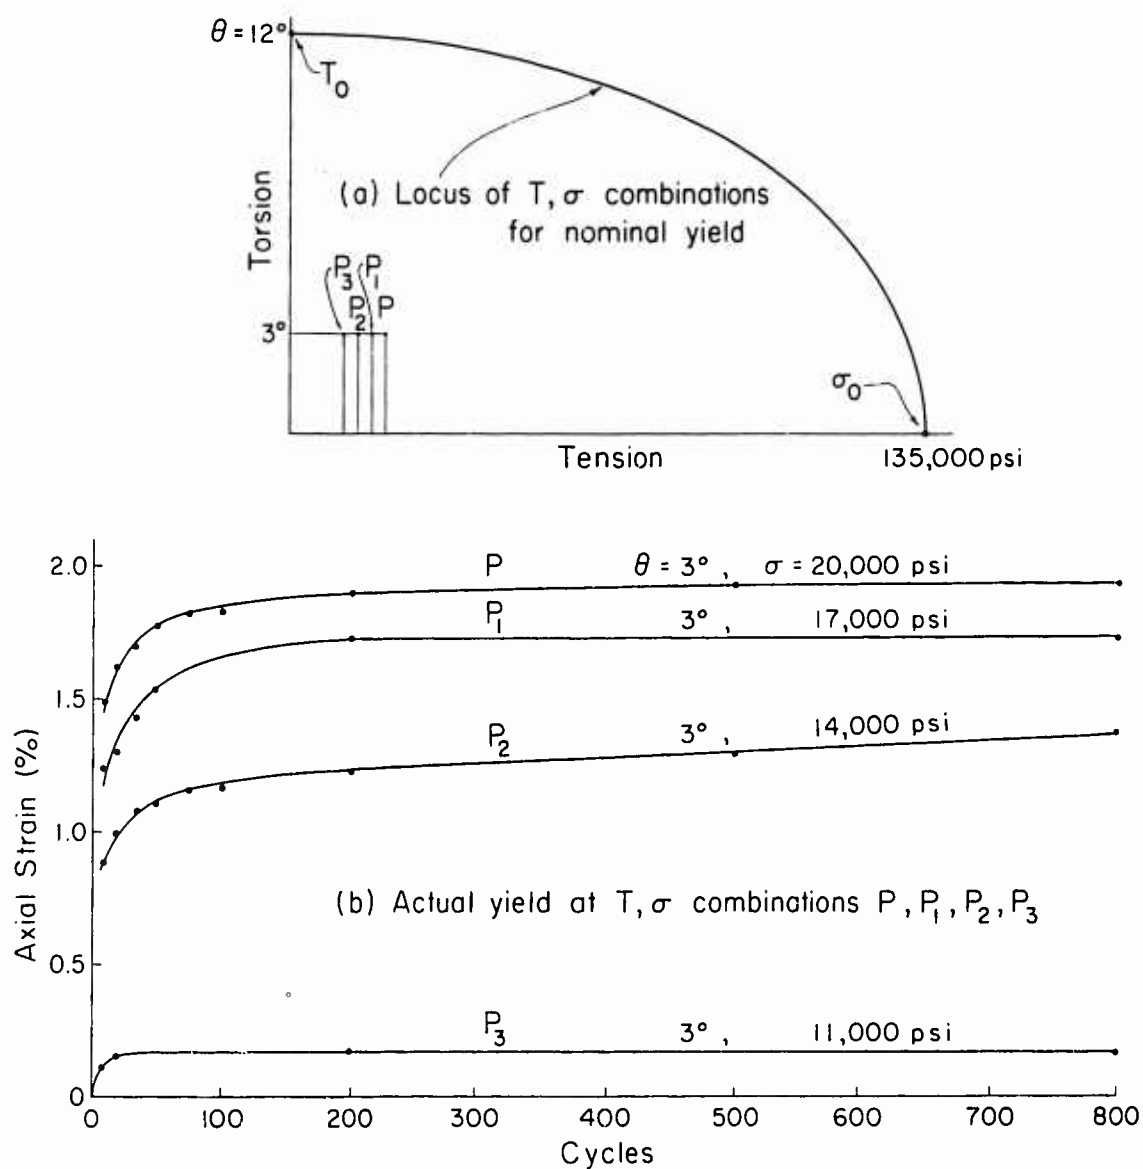


Fig. 5. (a) Schematic Mises ellipse; (b) Creep for points well within ellipse.

Ti/6Al/4V
no heat treatment

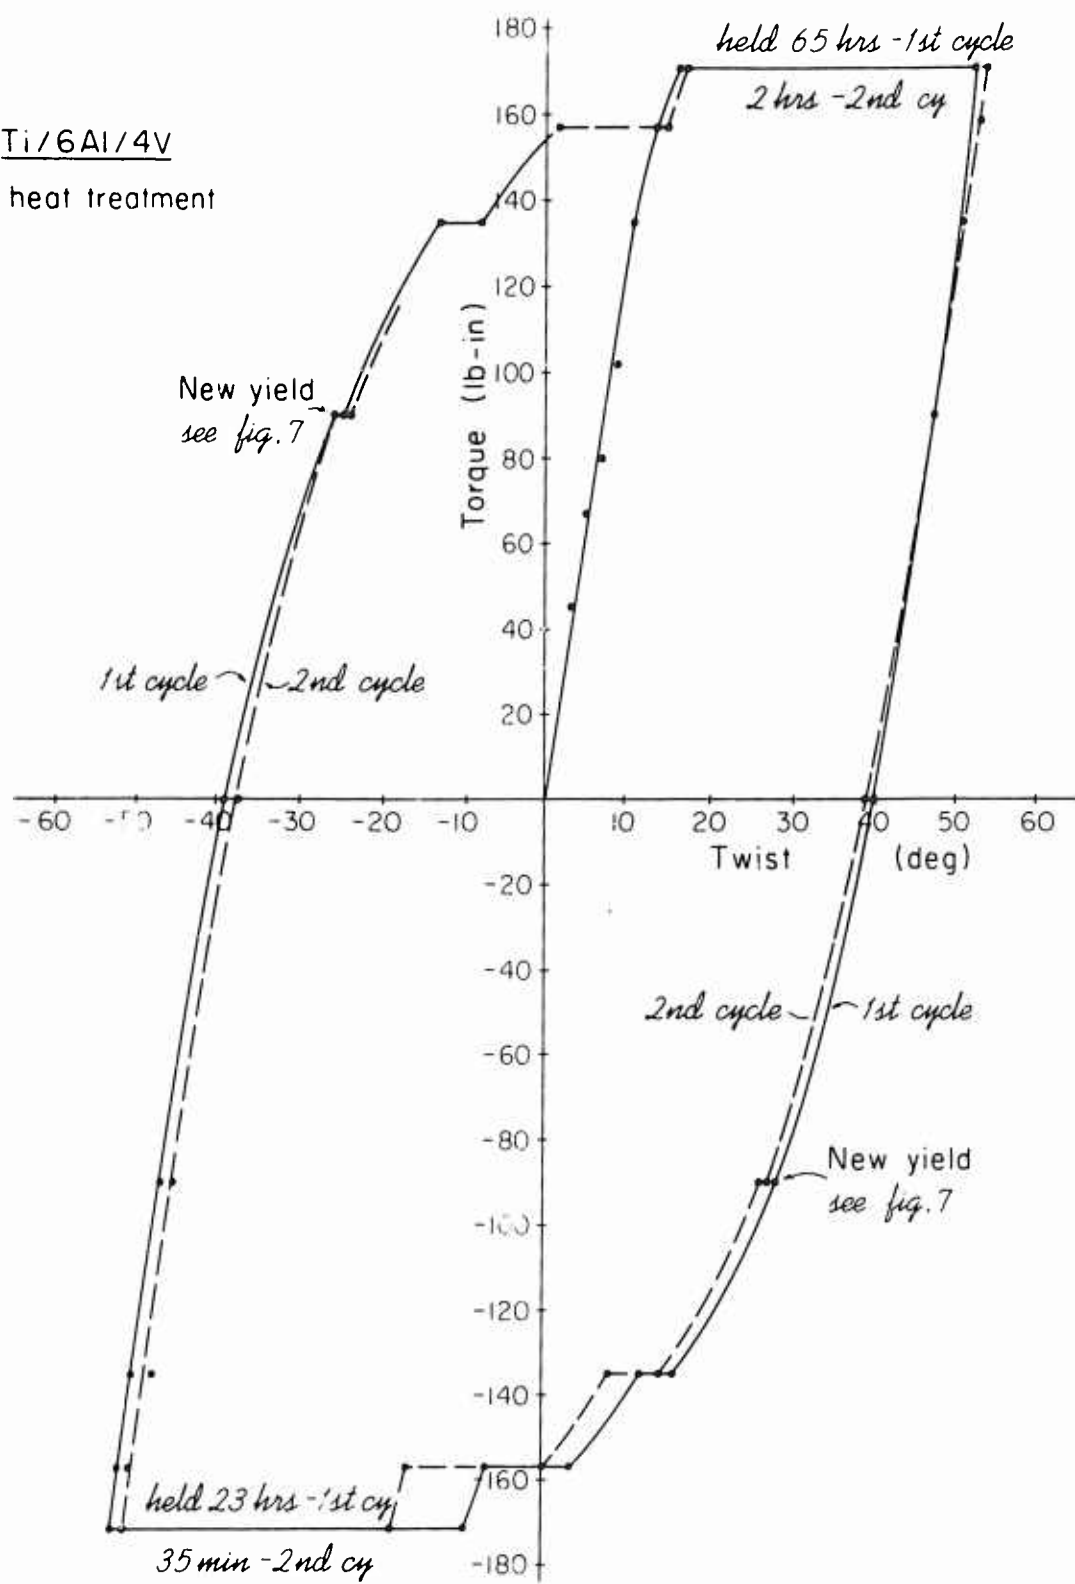


Fig. 6. Instability induced by large-amplitude cycles.

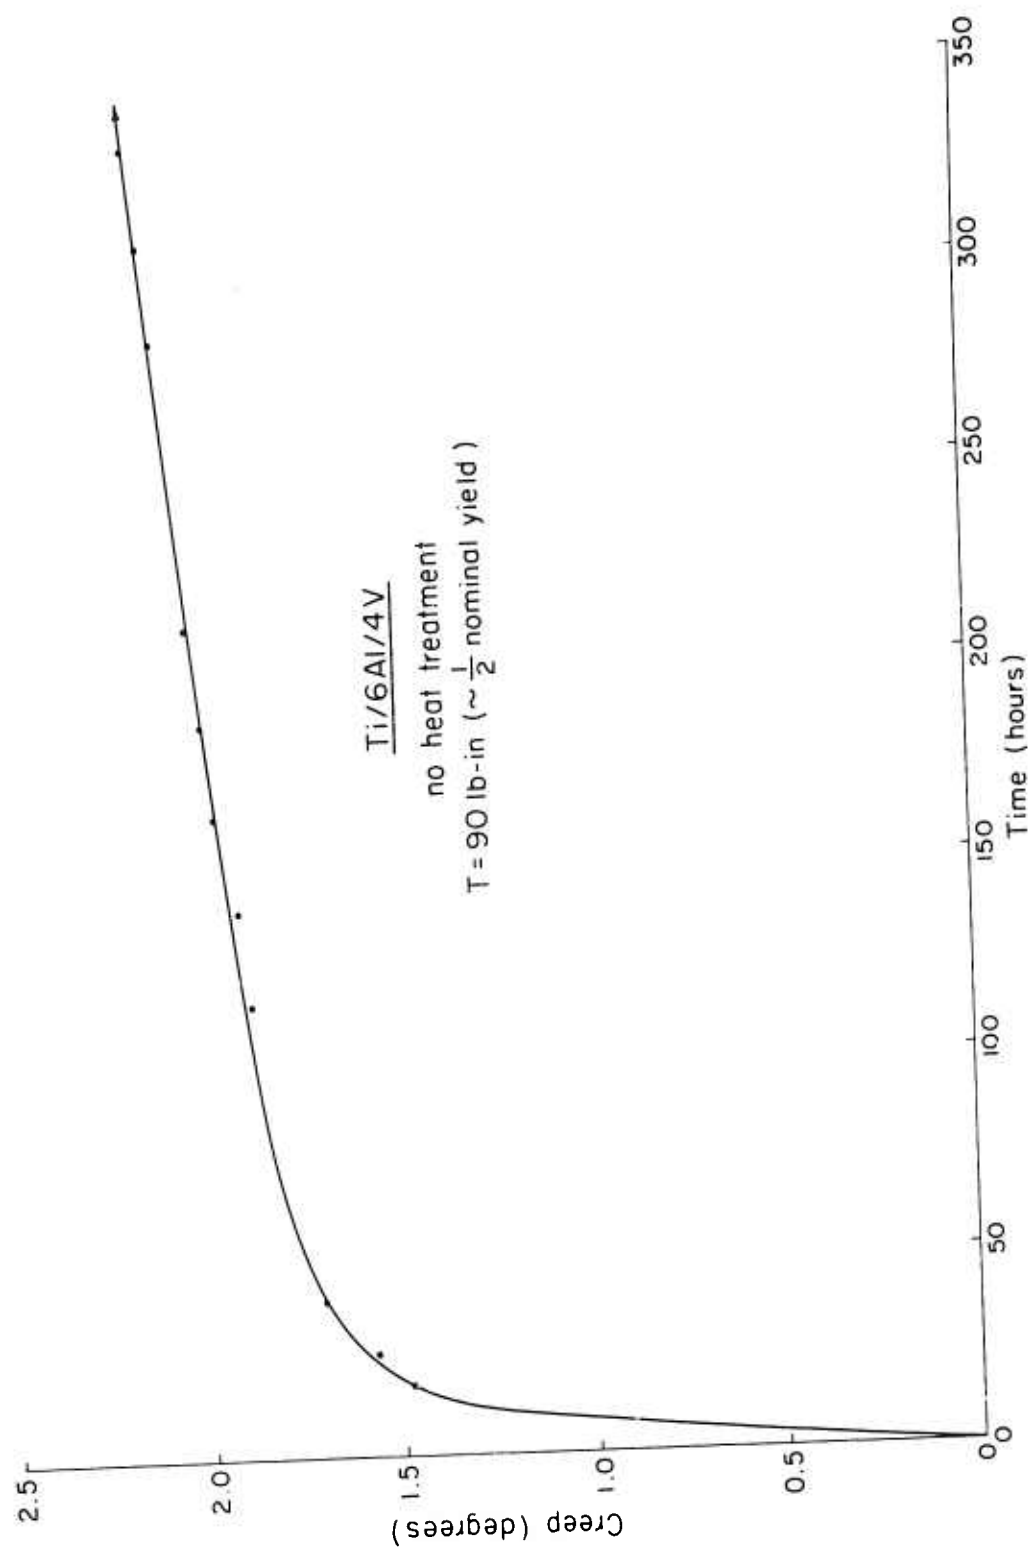


Fig. 7. Creep at yield reduced from 170 to 90 lb.-in. by pre-cycles.

Unclassified

Security Classification

DOCUMENT CONTROL DATA - R&D		
<small>(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)</small>		
1. ORIGINATING ACTIVITY (Corporate author) Department of Civil Engineering and Engineering Mechanics, Columbia University		2a. REPORT SECURITY CLASSIFICATION Unclassified
		2b. GROUP
3. REPORT TITLE Instability Of Titanium and Ti/6Al/4V Alloy at Room Temperature		
4. DESCRIPTIVE NOTES (Type of report and inclusive dates) Technical Report		
5. AUTHOR(S) (Last name, first name, initial) Wood, W. A.		
6. REPORT DATE April 1967	7a. TOTAL NO. OF PAGES 10	7b. NO. OF REFS -
8a. CONTRACT OR GRANT NO. Nonr 266 (91)	9a. ORIGINATOR'S REPORT NUMBER(S) Contract Nonr 266(91) Project No. NR 064-446 Report No. 45	
b. PROJECT NO. c. Nr 064-446 d.	9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)	
10. AVAILABILITY/LIMITATION NOTICES Qualified requesters may obtain this report from DDC		
11. SUPPLEMENTARY NOTES		12. SPONSORING MILITARY ACTIVITY Office of Naval Research
13. ABSTRACT <p>Titanium and Ti/6Al/4V under torsion exhibit unusual instability which shows itself as (a) abnormally prolonged creep on yielding, (b) ineffective strain-hardening after yielding, and (c) deviations from elastic strain at loads above a limit of proportionality which is low compared with the bulk yield stress. As a result of this inherent instability it is possible to produce significant axial extensions under low tensile stresses combined with small-amplitude cyclic torsion; and to reduce the nominal bulk yield stress in torsion to at least half its nominal value by suitable prior straining.</p>		

DD FORM 1473
1 JAN 64

Unclassified

Security Classification

Unclassified
Security Classification

14	KEY WORDS	LINK A		LINK B		LINK C	
		ROLE	WT	ROLE	WT	ROLE	WT
	Instability Titanium Titanium alloy						

INSTRUCTIONS

1. ORIGINATING ACTIVITY: Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (*corporate author*) issuing the report.
2. REPORT SECURITY CLASSIFICATION: Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.
- 2b. GROUP: Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.
3. REPORT TITLE: Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.
4. DESCRIPTIVE NOTES: If appropriate, enter the type of report, e.g., internal, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.
5. AUTHOR(S): Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.
6. REPORT DATE: Enter the date of the report as day, month, year, or month, year. If more than one date appears on the report, use date of publication.
- 7a. TOTAL NUMBER OF PAGES: The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.
- 7b. NUMBER OF REFERENCES: Enter the total number of references cited in the report.
- 8a. CONTRACT OR GRANT NUMBER: If appropriate, enter the applicable number of the contract or grant under which the report was written.
- 8b, c, & d. PROJECT NUMBER: Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.
- 9a. ORIGINATOR'S REPORT NUMBER(S): Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.
- 9b. OTHER REPORT NUMBER(S): If the report has been assigned any other report numbers (*either by the originator or by the sponsor*), also enter this number(s).
10. AVAILABILITY/LIMITATION NOTICES: Enter any limitations on further dissemination of the report, other than those

imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through _____."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through _____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. SUPPLEMENTARY NOTES: Use for additional explanatory notes.

12. SPONSORING MILITARY ACTIVITY: Enter the name of the departmental project office or laboratory sponsoring (*paying for*) the research and development. Include address.

13. ABSTRACT: Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. KEY WORDS: Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, roles, and weights is optional.